

Ion-size effects in cuprate superconductors - implications for pairing

B.P.P. Mallett,^{1,*} T. Wolf,² E. Gilioli,³ F. Licci,³ G.V.M. Williams,¹
A.B. Kaiser,¹ N.W. Ashcroft,⁴ N. Suresh,⁵ and J.L. Tallon⁵

¹MacDiarmid Institute, SPCS, Victoria University P.O. Box 600, Wellington 6140, New Zealand

²Karlsruhe Institute of Technology, Postfach 3640, Karlsruhe 76021, Germany

³IMEM-CNR, Institute of Materials for Electronics and Magnetism, 43124 Parma, Italy

⁴Laboratory of Atomic and Solid State Physics, Cornell University, Ithaca, N.Y. 14853-2501, U.S.A.

⁵MacDiarmid Institute, Industrial Research Limited, P.O. Box 31310, Lower Hutt, New Zealand.

(Dated: November 7, 2012)

The standard separation in metals between valence and core states leads in cuprate superconductors to constituent ions which may sustain both charge and spin fluctuations. We change ion size in $RA_2Cu_3O_y$ ($A=(Ba,Sr)$ and $R=(La, \dots Lu,Y)$) in order to systematically alter both dielectric and magnetic properties. Dielectric fluctuation is characterized by ionic polarizability while magnetic fluctuation is characterized by exchange interactions measurable by Raman scattering. The range of transition temperatures is 70 to 107 K and we find that these correlate only with the dielectric properties, a behavior which persists with external pressure. This highlights the fundamental importance of charge fluctuation and dielectric screening in the cuprates and may signal a novel pairing mechanism having its origin with quantized waves of electronic polarization.

The physical mechanism for electron pairing in cuprate superconductors remains uncertain. While there may be a broad consensus that it is probably magnetic in origin [1] a continuing challenge has been the apparent low spectral weight of associated spin fluctuations, as measured by inelastic neutron scattering [2]. Recent studies using inelastic x-ray scattering seem to locate the missing weight by identifying intense paramagnon excitations across the entire superconducting phase diagram [3]. If so then a key energy scale for pairing is, to leading order, the antiferromagnetic exchange interaction, J [3]. Consistent with this, Ofer *et al.* [4] correlated the T_c at optimal-doping, $T_c^{\max}$, with the Neel temperature, T_N , in the sex-enary system $(La_{1-x}Ca_x)(Ba_{1.75-x}La_{0.25+x})Cu_3O_y$. By modeling the anisotropy in the exchange interaction they found that $T_c^{\max}$ scaled with J .

We too examine such relationships in a simpler model system, $RA_2Cu_3O_y$ and we measure J directly using two-magnon Raman scattering. But we find quite the opposite result; $T_c^{\max}$ does not scale with J . Instead we find a strong correlation with the dielectric properties as described by the density-weighted sum of the ion polarizabilities (the refractivity sum). Something of this character might yet be explicable in a magnetic pairing scenario in terms of effective screening of long-range repulsive magnetic interactions [5]. But, it may also signal a novel pairing mechanism where the exchange boson is a quantized wave of electronic polarization [6].

We are motivated by what we consider a central paradox of high-temperature superconductor physics: external pressure increases $T_c^{\max}$ [7], whereas internal pressure, of chemical origin and as induced by isovalent ion substitution, decreases $T_c^{\max}$ [8, 9]. Fig. 1 shows $T_c^{\max}$ plotted against the composite bond valence sum (BVS) parameter, $V_+ = 6 - V_{Cu(2)} - V_{O(2)} - V_{O(3)}$, taken from ref. [8] (green squares). Here $V_{Cu(2)}$, $V_{O(2)}$ and $V_{O(3)}$ are the

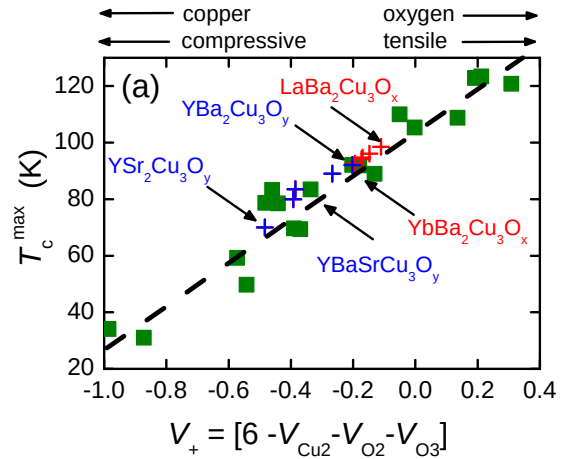


FIG. 1. [Color online] $T_c^{\max}$, plotted as a function of the bond valence sum parameter $V_+ = 6 - V_{Cu(2)} - V_{O(2)} - V_{O(3)}$. Green squares: as previously reported [8]; red crosses: for $RBa_2Cu_3O_y$ ($R = La, Nd, Sm, Gd, Dy$ and Yb); blue crosses: for $YBa_{2-x}Sr_xCu_3O_y$ ($x = 0, 0.5, 1.0, 1.25$ and 2).

planar copper and oxygen BVS parameters and the plot reveals a remarkable correlation of $T_c^{\max}$ across single-, two- and three-layer cuprates. Here V_+ was introduced as a measure of charge distribution between the Cu and O orbitals [10] but is also a measure of in-plane stress [11], as noted at the top of the figure. Evidently stretching the CuO_2 plane increases $T_c^{\max}$. However V_+ is a compound measure and also reflects physical displacement of the apical oxygen away from the Cu atoms.

Crucially, this plot reveals that all cuprates follow a systematic behavior. *There are no anomalous outliers.* It is common to regard $La_{2-x}Sr_xCuO_4$ as anomalous with

a marked propensity for disorder. But the left-most data point in Fig. 1 shows that it is entirely consistent with the other cuprates. It remains then to determine just what this V_+ parameter encapsulates so systematically.

To this earlier plot we now add new data for the compounds, $RA_2Cu_3O_y$, as R is varied (red crosses) and, in the case of $R = Y$, $A = Ba_{2-x}Sr_x$ where $x = 0, 0.5, 1, 1.25$ and 2 (blue crosses). We use the structural refinements of Guillaume *et al.* [12], Licci *et al.* [13] and Gilioli *et al.* [14] and calculate V_+ in the same way as previously [8]. Notably, the global correlation is also preserved across this model system, reflecting the progressive expansion of the lattice as ion size is increased. (We define ion size in terms of the effective radii discussed by Shannon [15]). Using the bulk compressibility these volume changes may be converted to an effective internal pressure and Fig. 1 thus summarizes a general feature of the cuprates, namely that internal pressure decreases $T_c^{\max}$. In contrast, as already noted, it is well known that external pressure increases $T_c^{\max}$ [7]. What then is the salient difference between internal and external pressure on $T_c^{\max}$?

The magnitude of $T_c^{\max}$ will be set in part by the energy scale, $\hbar\omega_B$, of the pairing boson and also by $N(E_F)$, the density of electronic states (DOS) at the Fermi-level. In the underdoped regime the DOS is progressively depleted by the opening of the pseudogap (with energy scale E_g), whereas in the overdoped regime it is enhanced by the encroaching proximity of the van Hove singularity (vHs). Our long-term goal is to study the comparative effects of internal and external pressure on the key variables, $T_c^{\max}$, ω_B , $N(E_F)$, E_g and $E_F - E_{vHs}$. Here we focus on ω_B which, if the pairing boson is a paramagnon, is governed to leading order by J [3].

We measured J in single crystals of $RBa_2Cu_3O_6$ (R-123) using B_{1g} two-magnon Raman scattering where the two-magnon peak occurs at $\omega_{\max} = 3.2J$ [16]. The normalized raw data shown in the inset to Fig. 2 reveal that, as the R ion-size decreases, the B_{1g} two-magnon peak shifts to higher frequency. This is expected because of the increased overlap between Cu $3d$ and O $2p$ orbitals.

The relative shift in effective internal pressure, ΔP_{eff} , may therefore be estimated from the change in unit cell volume, ΔV , using $\Delta P_{\text{eff}} = -B \cdot \Delta V / V_0$ where $B = 78.1$ GPa is the bulk modulus for deoxygenated $YBa_2Cu_3O_6$ [17] and $\Delta V = V - V_0$ is referenced to La-123. We plot $\omega_{\max}$ against ΔP_{eff} in the main panel of Fig. 2. Further, the dependence of J on basal area, A , is plotted in Fig. 3. To this internal pressure-effect data we also give in Fig. 3 the effect of external pressure on J in the related system La_2CuO_4 [18] (blue diamonds) ranging up to 10 GPa, as annotated. Remarkably, the dependence of J on A is preserved across the entire range, irrespective of whether the pressure is *internal* or *external* in origin. The inset shows that the same result is found for $YBa_2Cu_3O_{6.2}$ under external pressure now up to 80 GPa

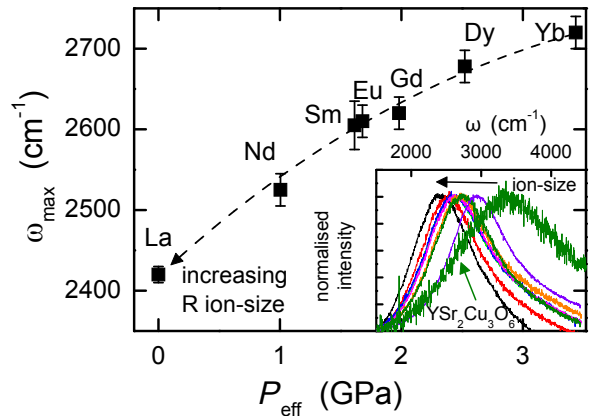


FIG. 2. [Color online] The B_{1g} Raman two-magnon peak position, $\omega_{\max}$, for each R-123 sample plotted against the effective internal pressure using $P_{\text{eff}} = -B \cdot \Delta V / V_0$ where $B = 78.1$ GPa is the bulk modulus [17] and $\Delta V = V - V_0$ is referenced to La-123. The inset shows normalized Raman spectra for R-123 single crystals and for polycrystalline $YSr_2Cu_3O_6$.

[19] (green diamonds) which projects directly onto our internal pressure data for R-123 (red squares). Collectively these cover a 60% increase in the magnitude of J arising from simple structural compression.

From Fig. 3 we conclude that external and internal pressure have similar effects on J . This is our first main result and it contrasts the opposing effects of internal and external pressure on $T_c^{\max}$. Accordingly, we now plot in Fig. 4 (a) $T_c^{\max}$ versus J for the R-123 single-crystal series (red squares) using $T_c^{\max} = 98.5$ K for La-123 [20] and $T_c^{\max} = 96$ K for Nd-123 [21] since these are the highest reported values of $T_c^{\max}$ in these compounds (where R occupation of the Ba site is minimized). Contrary to expectation, $T_c^{\max}$ anticorrelates with J when ion-size is the implicit variable.

To move to yet higher J values, we repeated the Raman measurements on a c -axis aligned thin film of $YBa_{1.5}Sr_{0.5}Cu_3O_6$ and on individual grains of polycrystalline $YSr_2Cu_3O_6$ prepared under high-pressure/high-temperature synthesis [14] (blue diamonds in Fig. 4 (a)). Significantly, the anticorrelation between $T_c^{\max}$ and J is preserved, but now out to a more than 60% increase in the value of J . This is a very large increase and it is surprising that it is not reflected in the value of $T_c^{\max}$ if magnetic interactions alone set the energy scale for pairing.

To this plot we add data showing the effect of external pressure on $T_c^{\max}$ and J in $YBa_2Cu_3O_7$ (green squares: for 1 bar and 1.7, 4.5, 14.5 and 16.8 GPa). The shift in J with pressure is taken from the inset to Fig. 3 and the values of $T_c^{\max}$ at elevated pressures are from refs [22, 23] - see Supporting Material [24]. We see that the shift in the data under external pressure is effectively orthogonal to that found under internal pressure and,

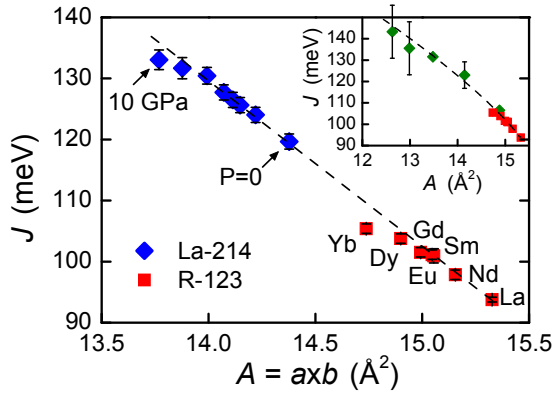


FIG. 3. [Color online] The basal area dependence of J determined from two-magnon scattering on $\text{R}\text{Ba}_2\text{Cu}_3\text{O}_6$ (red squares) where “internal pressure” is the implicit variable. The effect of external pressure [18] is also shown for La_2CuO_4 (0 to 10 GPa, blue diamonds). Remarkably a single behavior for $J(A)$ is preserved irrespective of whether the effective pressure is of internal or external origin. Inset: J versus A for pressure-dependent two-magnon data for $\text{YBa}_2\text{Cu}_3\text{O}_{6.2}$ to 80 GPa [19] (green diamonds) compared with our ion-size-dependent data for $\text{R}\text{Ba}_2\text{Cu}_3\text{O}_6$ (red squares).

again, highlights the fact that the observed shifts in J simply do not correlate with T_c^{max} . This is our second main result.

As noted these results differ from Ofer *et al.* [4] who reported correlations between T_c^{max} and the Néel temperature, T_N , in $(\text{La}_{1-x}\text{Ca}_x)(\text{Ba}_{1.75-x}\text{La}_{0.25+x})\text{Cu}_3\text{O}_y$. However, the effects they report are quite small compared with ours. Moreover, since T_N is not directly related to J their analysis required a model to estimate the exchange anisotropy and thereby convert T_N to J . We also note that this complex system has large nuclear quadrupole resonance linewidths reflecting a high degree of disorder. It is our view that the present study is more direct and reliable in its implications.

We note that B_{1g} scattering only probes nearest-neighbor magnetic interactions [25] while recent inelastic x-ray scattering studies [26] reveal the presence of extended interactions involving next-nearest- and next-next-nearest-neighbor hopping integrals, t' and t'' [27]. The additional extended exchange interaction is only about half the magnitude of the changes that we have imposed by ion-size variation. It is conceivable that inclusion of extended interactions might reverse the systematics reported here, however, it is our view that variations in t' and t'' will have a stronger influence via the DOS by distorting the Fermi surface and shifting the vHs.

Our observations suggest two possibilities, either that (i) the pairing energy scale is in fact unrelated to J , or, (ii) pairing may be governed by magnetic interactions but

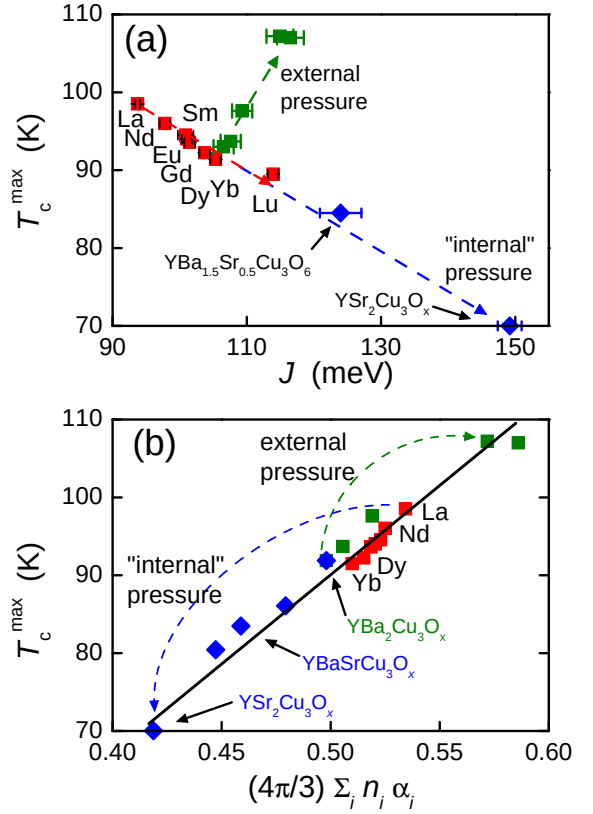


FIG. 4. [Color online] (a) T_c^{max} is plotted versus J for single crystals of $\text{R}\text{Ba}_2\text{Cu}_3\text{O}_6$ (red squares) and for $\text{YBa}_{2-x}\text{Sr}_x\text{Cu}_3\text{O}_6$ (blue diamonds) with $x = 0.5$ and 2.0 . T_c^{max} anticorrelates with J where ion size or “internal pressure” (blue trajectory) is the implicit variable. The green squares show that T_c^{max} versus J under external pressure (green trajectory) is effectively orthogonal to the behavior for internal pressure. (b) T_c^{max} plotted against the polarizability sum $(4\pi/3)\sum_i n_i \alpha_i$ for $\text{R}\text{Ba}_2\text{Cu}_3\text{O}_y$ (red squares, $\text{R} = \text{La}, \text{Nd}, \text{Sm}, \text{Eu}, \text{Gd}, \text{Dy}, \text{Yb}$) and $\text{YBa}_{2-x}\text{Sr}_x\text{Cu}_3\text{O}_6$ (blue diamonds, $x = 0, 0.5, 1.0, 1.25$ and 2) which summarize the effects of “internal pressure”. The green squares show T_c^{max} versus $(4\pi/3)\sum_i n_i \alpha_i$ for $\text{YBa}_2\text{Cu}_3\text{O}_y$ under external pressure, revealing a correlation which remains consistent with that for internal pressure.

other energy scales also vary across the R-123 series and have a much larger effect on T_c^{max} than J does.

However, we must bear in mind the simplicity of the systematic evolution of T_c^{max} shown in Fig. 1 and the above results suggest we may have to look elsewhere to locate its underlying origins. One arena where ion-size plays a key role is in the dielectric properties, where the ionic polarizability varies roughly as the cube of the ion size [15]. This suggests an alternative and relatively unexplored possibility, namely, that pairing in the multi-ion cuprates might be attributable in large measure to

the exchange of bosons associated with coherent quantized waves of polarization - a direct analog of quantized waves of ionic displacement as they occur in the familiar phonon pairing picture [6, 28]. We explore this in more detail:

The isolated CuO_2 planar array is electrostatically uncompensated and as such cannot constitute a thermodynamic system. It is necessary to include the compensating charges lying outside of the CuO_2 plane in any thermodynamic treatment and these will also contribute to electron-electron interactions within the plane. These charges also reside on ions that are notably polarizable, and they contribute to the high background dielectric constants observed in the cuprates [29]. Atwal and Ashcroft [6] have shown that the polarization-wave pairing channel in a highly polarizable medium can be dominant. In an early treatment of this problem Goldhammer [30] showed for sufficiently symmetric systems that the dielectric constant contains a factor $[1 - \frac{4\pi}{3} \sum_i n_i \alpha_i]^{-1}$ leading in principle to polarization catastrophe. Here the sum is over all ions i , n_i are the volume densities of these ions and α_i their polarizabilities. (The factor $\frac{4\pi}{3}$ is ultimately dependent on structure, the dielectric constant more generally being replaced by a dielectric matrix; and in a fuller treatment the enhancement factor is replaced by frequency- and momentum-dependent terms [6]).

Here we focus just on the contributions from the non-cuprate layers and in Fig. 4 (b) we plot T_c^{max} versus $\frac{4\pi}{3} \sum_i n_i \alpha_i$ for $\text{R}(\text{Ba}, \text{Sr})_2\text{Cu}_3\text{O}_7$ where the sum is over R, Ba, Sr, and the apical O(4) oxygens. Red squares summarize the effects of changing R and blue diamonds the effects of progressively replacing Ba by Sr. These are the “internal” pressure effects and the correlation is excellent. The polarizabilities are taken from Shannon [15]. Moreover, this also resolves the paradox of the opposing effects of internal and external pressure. Increasing ion size (decreasing internal pressure) increases the polarizability while increasing external pressure enhances the densities n_i , in both cases increasing the dielectric enhancement factor. To test this we also plot T_c^{max} versus $\frac{4\pi}{3} \sum_i n_i \alpha_i$ for $\text{YBa}_2\text{Cu}_3\text{O}_7$ at 1 bar and 1.7, 4.5, 14.5 and 16.8 GPa (green squares) where we have assumed to first order that only the n_i , and not the α_i , alter under pressure. For more details see [24]. The correlation with polarizability is now preserved over a range of T_c^{max} from 70 K to 107 K, including both internal and external pressure. This is our third main result and it also now links to the correlation with V_+ shown in Fig. 1. The additional role of the apical oxygen bond length (which contributes to the value of V_+) has yet to be clarified, but it possibly plays a supplementary role in controlling the large polarizability of the Zhang-Rice singlet [31].

What may we conclude? A highly polarizable medium could merely be effective in screening long-range magnetic interactions, which tend to be repulsive [5]. An

increasing polarizability sum would then increase T_c , as observed. Perhaps even more interestingly, coherent fluctuations of this medium, quantized waves of polarization, may in fact be the elusive exchange boson which binds the Cooper pairs [6]. Both these scenarios can be tested.

Finally, based on our observed correlation and an inferred polarizability of $\alpha_{\text{Ra}} = 8.3 \text{ \AA}^3$ for the Radium ion, Ra^{2+} [24], we deduce an implied T_c^{max} of $109 \pm 2 \text{ K}$ for $\text{YRa}_2\text{Cu}_3\text{O}_y$ and $117 \pm 2 \text{ K}$ for $\text{LaRa}_2\text{Cu}_3\text{O}_y$. Similarly, T_c^{max} for $\text{HgRa}_2\text{Ca}_2\text{Cu}_3\text{O}_8$ should be about 150 K. Again, these inferences can be tested, though they are not without their challenges!

In summary, we have shown that the characteristic exchange energy scale, J , increases as the ion size in $\text{RBa}_{2-x}\text{Sr}_x\text{Cu}_3\text{O}_y$ decreases. Furthermore, the influence of this effective *internal* pressure on J is quantitatively similar to the effect of *external* pressure on J across a very wide range of compression. This is to be contrasted with the opposite effects of internal and external pressure on T_c^{max} . We find that T_c^{max} anticorrelates with J when ion size is the implicit variable which suggests some energy scale other than that arising from short-range magnetic interactions has a more prominent effect on T_c^{max} . Instead, we find that T_c^{max} correlates exceptionally well with the weighted sum of the polarizabilities of the charge-transfer layers, both for internal and external pressures. This may signal an altogether different pairing mechanism involving coherent collective excitations associated with the ionic polarizabilities.

The authors acknowledge funding from The Marsden Fund (GVMW, NS, JLT), the MacDiarmid Institute (BPPM, JLT) and the National Science Foundation, DMR-0907425 (NWA).

* Corresponding author, b.mallett@irl.cri.nz

- [1] Scalapino, D.J., Rev. Mod. Phys. **84**, 1383 (2012).
- [2] Maksimov, E.G., Kulić, M.L. and Dolgov, O.V., Adv. Cond. Mat. Phys. **2010**, 423725 (2010).
- [3] M. Le Tacon, et al. Nature Physics **7**, 725 (2011).
- [4] R. Ofer, G. Bazalitsky, A. Kanigel, A. Keren, A. Auerbach, J. S. Lord, and A. Amato, Phys. Rev. B **74**, 220508 (2006).
- [5] S. Raghu, R. Thomale, and T. H. Geballe, Phys. Rev. B **86**, 094506 (2012).
- [6] G.S. Atwal and N.W. Ashcroft, Phys. Rev. B **70**, 104513 (2004).
- [7] J. Schilling, in Handbook of High-Temperature Superconductivity, ed by J. Schrieffer and J. Brooks (Springer New York, 2007) pp. 427-462.
- [8] J. L. Tallon, Physica C **168**, 85 (1990).
- [9] M. Marezio, E. Gilioli, P. Radaelli, A. Gauzzi, and F. Licci, Physica C **341**, 375 (2000).
- [10] I. Brown and D. Altermatt, Acta Cryst. B **41**, 244 (1985).
- [11] I. Brown, J. Solid State Chem. **82**, 122 (1989).
- [12] M. Guillaume, et al. J. Phys. Cond. Mat. **6**, 7963 (1994).
- [13] F. Licci, A. Gauzzi, M. Marezio, G. P. Radaelli, R.

- Masini, and C. Chaillout-Bougerol, Phys. Rev. B **58**, 15208 (1998).
- [14] E. Gilioli, P. Radaelli, A. Gauzzi, F. Licci, and M. Marezio, Physica C **341**, 605 (2000).
 - [15] R. Shannon, J. App. Phys. **73**, 348 (1993).
 - [16] A. V. Chubukov and D. M. Frenkel, Phys. Rev. B **52**, 9760 (1995).
 - [17] K. Suenaga and G. Oomi, J. Phys. Soc. Japan **60**, 1189 (1991).
 - [18] M.C. Aronson, S.B. Dierker, B.S. Dennis, S.W. Cheong, and Z. Fisk, Phys. Rev. B **44**, 4657 (1991).
 - [19] A. Maksimov and I. Tartakovskii, J. Superconductivity **7**, 439 (1994).
 - [20] T. Lindemer, B. Chakoumakos, E. Specht, R. Williams, and Y. Chen, Physica C **231**, 80 (1994).
 - [21] B. Veal, *et al.* Physica C **162**, 97 (1989).
 - [22] M. McElfresh, M. Maple, K. Yang, and Z. Fisk, App. Phys. A **45**, 365 (1988).
 - [23] S. Sadewasser, J.S. Schilling, A.P. Paulikas, and B.W. Veal, Phys. Rev. B **61**, 741 (2000).
 - [24] B.P.P. Mallett, *et al.* Supporting Material, *to be uploaded to arXiv*.
 - [25] R.R.P. Singh, P.A. Fleury, K.B. Lyons, and P.E. Sulewski, Phys. Rev. Lett. **62**, 2736 (1989).
 - [26] M. Guarise, *et al.* Phys. Rev. Lett. **105**, 157006 (2010).
 - [27] E. Pavarini, I. Dasgupta, T. Saha-Dasgupta, O. Jepsen, and O. K. Andersen, Phys. Rev. Lett. **87**, 047003 (2001).
 - [28] N. Ashcroft, in Novel Superconductivity, ed by S. Wolf and V. Kresin (Plenum Press, New York, NY, 1987).
 - [29] D. Reagor, E. Ahrens, S.W. Cheong, A. Migliori, and Z. Fisk, Phys. Rev. Lett. **62**, 2048 (1989).
 - [30] D. Goldhammer, B.G. Teubner, Leipzig, Germany (1913).
 - [31] F.C. Zhang and T.M. Rice, Phys. Rev. B, **37**, 3759 (1988).

Supporting material for: Ion-size effects in cuprate superconductors – implications for pairing

B.P.P. Mallett^{1†}, T. Wolf², E. Gilioli³, F. Licci³, G.V.M. Williams¹, A.B. Kaiser¹, N. Suresh⁴, N.W. Ashcroft⁵, J.L. Tallon⁴

¹MacDiarmid Institute, SPCS, Victoria University P.O. Box 600, Wellington 6140, New Zealand

²Karlsruhe Institute of Technology, Inst. Solid State Physics, P.O. Box 3640, D-76021 Karlsruhe, Germany

³IMEM-CNR, Institute of Materials for Electronics and Magnetism, 43124 Parma, Italy

⁴MacDiarmid Institute, Industrial Research Limited, P.O. Box 31310, Lower Hutt, New Zealand

⁵Laboratory of Atomic and Solid State Physics, Cornell University, Ithaca, N.Y.14853-2501, U.S.A.

1. Method.

High-quality $\text{RBa}_2\text{Cu}_3\text{O}_{7-\delta}$ single crystals were flux grown in Y-stabilized zirconia crucibles under reduced oxygen atmosphere, where necessary, to avoid substitution of R ions on the Ba site. The crystals were annealed for three days in flowing Ar at 600°C to remove oxygen from the chains then quenched to room temperature while still under Ar gas. We expect $\delta \geq 0.97$ from these annealing conditions and the measured mass change. Fully de-oxygenated chains are inert and this should eliminate any internal pressure-induced charge transfer that could otherwise occur between chain and CuO_2 layers. Moreover, even if there is some residual oxygen in the chains the doping state remains zero provided the oxygens remain isolated and chain segments do not start to form [1]. Well-oriented films of $\text{Y}(\text{Ba}_{1-x}\text{Sr}_x)_2\text{Cu}_3\text{O}_{7-\delta}$ were synthesised by metallo-organic deposition on $\text{RaBITS}^{\text{TM}}$ textured Ni/W substrates with epitaxial buffer layers of $\text{Y}_2\text{O}_3/\text{YSZ}/\text{CeO}_2$. Polycrystalline samples of $\text{YSr}_2\text{Cu}_3\text{O}_{7-\delta}$ were prepared at 3 GPa and 1050°C using a multi-anvil apparatus with KClO_3 as an oxidant [2].

Raman measurements were made at ambient temperature using a LabRam confocal microscope Raman spectrometer in back-scattering B_{1g} geometry. For all samples except the polycrystalline $\text{YSr}_2\text{Cu}_3\text{O}_6$ the B_{2g} , $A_{1g}+B_{2g}$ and $A_{1g}+B_{1g}$ scattering geometries were used to check we were indeed measuring two-magnon scattering. The 514.5 nm line from an Ar ion laser with power $\leq 1\text{mW}$ was focused to a spot of size $\sim 1\mu\text{m}$. A 300 lines/mm diffraction grating was used to capture the two-magnon peak in a single frame. For data in the inset to Fig. 2 we subtract a flat background, then normalise by the maximum in the scattering response.

2. Synopsis of results

We vary the nearest-neighbour superexchange interaction, J , (as measured by two-magnon Raman scattering) by more than 60% by changing ion sizes in $\text{RA}_2\text{Cu}_3\text{O}_{7-\delta}$, where $A=(\text{Ba},\text{Sr})$ and $R=(\text{La}, \dots \text{Lu}, \text{Y})$. Surprisingly, we find T_c^{max} anticorrelates with J (Fig. 4(a)), suggesting that J is not the dominant energy scale governing T_c^{max} , and possibly signalling an additional, or even alternative, pairing mechanism. The fact that T_c^{max} directly correlates with the mean polarizability of the R and (Ba,Sr)O layers (Fig. 4(b)) suggests that either:

- (i) the highly polarizable medium screens long-range repulsive magnetic interactions, or
- (ii) polarization waves could be the elusive pairing boson that mediates superconductivity in HTS cuprates.

3. Other studies

Our results may appear to be at odds with another Raman study where it is reported that, with increasing doping, the B_{1g} gap parameter observed in low-frequency Raman scattering is proportional to J [3]. But it is important to note that the B_{1g} gap is not the SC order parameter, Δ_0 . B_{1g} probes anti-nodal regions of the Fermi-surface [4,5] so will contain contributions from both the pseudogap, E_g , and Δ_0 , and in the under-doped region is completely dominated by E_g . Consequently, this reported correlation of the B_{1g} gap with J does not imply a link between J and Δ_0 but, rather, establishes a direct correlation between E_g and J as has already been inferred from specific heat [6] and inelastic neutron scattering [7]. It is the low-frequency B_{2g} gap feature which probes Δ_0 [4,5] and this does not correlate with J .

4. Choice of doping state

It has previously been found that J is quite strongly doping dependent, in the case of $\text{Bi}_2\text{Sr}_2\text{Ca}_{1-x}\text{Y}_x\text{O}_{8-y}$ falling more or less linearly with doping from 125 meV in the undoped insulator to 45 meV in the lightly overdoped region at 0.20 holes/Cu [8]. Because of this strong doping dependence we focus on the undoped insulator (O_6) because this is the only reproducible doping state for intercomparison of the different lanthanides. And perhaps more importantly, we wish to avoid pressure-induced charge transfer which can only be assured when the CuO chains are fully deoxygenated.

In the light of this, is the observed shift in J merely an inadvertent doping effect? We believe not, for the following reasons:

- (i) As discussed above, for low oxygen concentration in the chain layer of R123, $\delta \approx 1$, the CuO_2 planes are undoped and, in fact, insensitive to small changes in the oxygen concentration [9].
- (ii) We have recently measured the pressure dependence of the thermopower of deoxygenated $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_3\text{O}_6$ and there is no evidence of pressure-induced charge transfer [10]. Typically when $\delta < 1$ the application of pressure results in a strong decrease in the thermopower [11] reflecting an increase in doping state [12]. However when the samples are near fully deoxygenated ($\delta \approx 1$) the thermopower becomes pressure independent.
- (iii) If $\delta < 1$ then for a given δ the doping on the CuO_2 planes increases with decreasing ion size in the R123 system [13]. Given that J decreases as doping is increased [8], this would have the effect of J decreasing with decreasing ion size, the opposite to what we report.

5. Spin-charge stripes at large J ?

There is the question as to whether the large values of J in the strongly-compressed structures exemplified by $\text{YBa}_{2-x}\text{Sr}_x\text{Cu}_3\text{O}_x$ merely promote spin-charge stripes similar to what occurs in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$, thereby reducing T_c despite a magnetic pairing scenario which should otherwise raise T_c . We believe this is demonstrably not the case. In Fig. S1 we reproduce Fig. 4(a) but now include the data for $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$. It remains a stark outlier, with J mid-range but $T_c^{\text{max}} = 39$ K. For $\text{YSr}_2\text{Cu}_3\text{O}_x$ the value of J well exceeds that for $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ yet T_c remains high. This shows again that J is not the dominant player. We believe that our model system remains well behaved across the full range of J . Moreover, $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ fits the correlation in Fig. 1 (as shown by the left-most data point) as does $\text{YSr}_2\text{Cu}_3\text{O}_x$. This shows that there is some feature other than the magnitude of J , but reflected rather by the value of V_+ , that determines their respective T_c^{max} values. We have suggested that it is the ionic polarizability that at least partly governs the magnitude of T_c^{max} . Indeed, the parameter V_+ is

governed by the stretch of the in-plane Cu-O bond and the Cu-apical-oxygen bond length. These are controlled by the ion sizes in the block layers which in turn govern the ionic polarizability.

6. Pressure dependence of J and $T_c^{\max}$

Under ambient pressure $T_c^{\max}$ for $\text{YBa}_2\text{Cu}_3\text{O}_x$ is close to 93 K. To find $T_c^{\max}$ at higher pressures it is important to note that the application of pressure has two effects: (i) to raise the magnitude of $T_c^{\max}$ and (ii) pressure-induced charge transfer which increases the hole doping state. Thus to determine $T_c^{\max}$ at elevated pressure one must investigate underdoped $\text{YBa}_2\text{Cu}_3\text{O}_x$. The closer is the system to optimal doping (on the underdoped side) the lower the pressure needed to attain optimal doping and $T_c^{\max}$ rises little above its ambient pressure value. But as the underdoping is increased, higher pressures are required to reach optimum doping and $T_c^{\max}$ is raised further. This applies until the 60 K plateau is attained around $p \approx 0.125$, when this pattern is broken and very much lower values of $T_c^{\max}$ are then encountered [14]. Unfortunately no report has yet been presented of these systematics in small increments of doping. This is a gap that needs to be filled. However there are enough reports at several doping states to confirm the pattern. We then have the following data: ($P = 1$ bar, $T_c^{\max} = 93$ K); ($P = 1.7$ GPa, $T_c^{\max} = 93.7$ K [14]); ($P = 4.5$ GPa, $T_c^{\max} = 97.6$ K [15]); ($P = 14.5$ GPa, $T_c^{\max} = 107.2$ K [16]); and ($P = 16.8$ GPa, $T_c^{\max} = 107$ K [14]).

For each of these pressures the value of J is determined for $\text{YBa}_2\text{Cu}_3\text{O}_x$ from the inset to Fig.3, interpolating on a simple proportional basis. We obtain: ($P = 1$ bar, $J = 106.5$ meV); ($P = 1.7$ GPa, $J = 107.6$ meV); ($P = 4.5$ GPa, $J = 109.3$ meV); ($P = 14.5$ GPa, $J = 114.9$ meV);

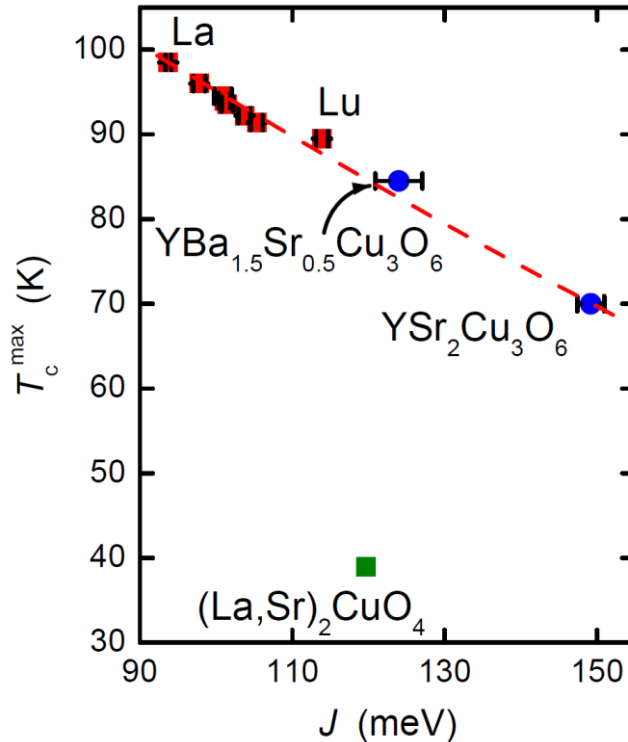


Figure S1. A reproduction of Fig. 4(a) showing ion-size effects on $T_c^{\max}$ and J in the model system $\text{RA}_2\text{Cu}_3\text{O}_x$ but now including $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$. The fact that the latter compound is a stark outlier when its J value is only mid-range suggests that it is not the large value of J which promotes “stripes” and suppresses $T_c^{\max}$.

and ($P = 16.8$ GPa, $J = 116.5$ meV). From these, the values of $T_c^{\max}$ are plotted versus J (with P as the implicit variable) by the green squares in Fig. 4(a).

7. Pressure dependence of $\sum_i n_i \alpha_i$

We assume to a first approximation that the effect of pressure is predominantly in the magnitude of n_i which just scales as the density. Thus, defining $S = \sum_i n_i \alpha_i$, and $S_0 = S(P=0)$, then $S(P) = S_0 \times V_0/V = S_0 / (1 - P/B)$ where, again, B is the isothermal bulk modulus. Because these calculations are applied at optimal doping we must use the bulk modulus for fully oxygenated $\text{YBa}_2\text{Cu}_3\text{O}_7$, namely, $B = 112$ GPa [17]. We obtain: ($P = 1$ bar, $S_0 = 0.1189$, $T_c^{\max} = 93$ K); ($P = 1.7$ GPa, $S = 0.1207$, $T_c^{\max} = 93.7$ K); ($P = 4.5$ GPa, $S = 0.1239$, $T_c^{\max} = 97.6$ K); ($P = 14.5$ GPa, $S = 0.1365$, $T_c^{\max} = 107.2$ K); and ($P = 16.8$ GPa, $S = 0.1399$, $T_c^{\max} = 107$ K). These values of $T_c^{\max}$ and $S(P)$ are plotted in Fig. 4(b) by the green squares which reveal a continuity with the data where internal pressure or ion size is the implicit variable.

8. Estimation of $T_c^{\max}$ for $\text{A} = \text{Radium}$

The progression of $T_c^{\max}$ with ion size (either with $\text{Lu} \rightarrow \text{La}$, or $\text{Sr} \rightarrow \text{Ba}$) suggests that replacement of Ba^{2+} with Ra^{2+} will continue this progression. The ionic polarizability of Ra^{2+} does not seem to be reported in the literature so we simply used the fact that, to a good approximation, $\alpha_i \sim r_i^3$. In Fig. S2 we plot the polarizabilities for the alkali-earth ions as reported by Shannon [18]. The ion radii are from Shannon [19]. The $\alpha_i \sim r_i^3$ dependence is apparent and suggests, if continued, $\alpha_i(\text{Ra}^{2+}) = 8.03 \text{ \AA}^3$. Based on an extrapolation of Fig.4(b) this leads to a projected $T_c^{\max}$ of 109 ± 2 K for $\text{YRa}_2\text{Cu}_3\text{O}_x$ and about 117 ± 2 K for $\text{LaRa}_2\text{Cu}_3\text{O}_x$.

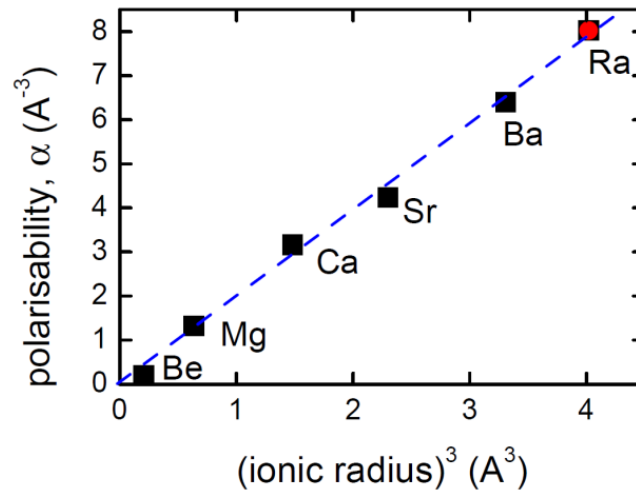


Figure S2. The ionic polarizability plotted versus cube of the ionic radius in order to estimate $\alpha(\text{Ra}^{2+}) = 8.03 \text{ \AA}^3$. Polarizabilities are from ref. [18] and ionic radii from ref. [19].

References for Supporting Material:

1. Alloul, H., Mendels, P. Collin, G. & Monod, P. ^{89}Y NMR Study of the Pauli Susceptibility of the CuO_2 Planes in $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$. *Phys. Rev. Lett.*, **61**, 746-749 (1988).
2. Gilioli, E., Radaelli, P.G., Gauzzi, A. Licci, F. & Marezio, M., Structure and Superconductivity of $\text{YSr}_2\text{Cu}_3\text{O}_{7-d}$. *Physica C: Superconductivity*, **341**, 605-606 (2000).
3. Sugai, S. & Hosokawa, T. Relation between the Superconducting Gap Energy and the Two-Magnon Raman Peak Energy in $\text{Bi}_2\text{Sr}_2\text{Ca}_{1-x}\text{Y}_x\text{Cu}_2\text{O}_{8+y}$. *Phys. Rev. Lett.*, **85**, 1112-1115 (2000).
4. Guyard et al., Temperature Dependence of the Gap Size near the Brillouin-Zone Nodes of $\text{HgBa}_2\text{CuO}_4$ Superconductors. *Phys. Rev. Lett.*, **101**, 097003 (2008).
5. LeBlanc, J. P. F., Carbotte, J. P., & Nicol, E. J., Signatures of Fermi surface reconstruction in Raman spectra of underdoped cuprates. *Phys. Rev. B*, **81**, 064504 (2010).
6. Loram, J.W., Luo, J. Cooper, J. R., Liang, W.Y. & Tallon, J. Evidence on the pseudogap and condensate from the electronic specific heat. *Journal of Physics and Chemistry of Solids*, **62**, 59-64 (2001).
7. Storey, J., Tallon, J. & Williams, G. Pseudogap ground state in high-temperature superconductors. *Phys. Rev. B*, **78**, 140506(R) (2008).
8. Sugai, S., Suzuki, H., Takayanagi, Y., Hosokawa, T., & Hayamizu, N., Carrier-density-dependent momentum shift of the coherent peak and the LO phonon mode in p -type high- T_c superconductors, *Phys. Rev. B*, **68**, 184504 (2003)
9. Tallon, J. L., Bernhard, C., Shaked, H., Hitterman, R. L. & Jorgensen, J. D., Generic superconducting phase behavior in high- T_c cuprates: T_c variation with hole concentration in $\text{YBa}_2\text{Cu}_3\text{O}_{7-y}$, *Phys. Rev. B*, **51**, 12911 (1995)
10. Argenijevic, S., Forro, L. & Tallon, J.L., Unpublished.
11. Zhou, J. -S. & Goodenough, J. B., Pressure dependence of thermopower in $\text{YBa}_2\text{Cu}_3\text{O}_{6.96}$ and $\text{YBa}_2\text{Cu}_4\text{O}_8$, *Phys. Rev. B*, **53**, 11976(R) (1996).
12. Obertelli, S. D., Cooper, J. R. & Tallon, J. L. Systematics in the thermoelectric power of high- T_c oxides, *Phys. Rev. B*, **46**, 14928 (1992)
13. Samoylenkov, S.V., Gorbenko, O. Yu. & Kaul, A.R., An analysis of charge carriers distribution in $\text{RBa}_2\text{Cu}_3\text{O}_7$ using the calculation of bond valence sums, *Physica C*, **278**, 49 (1997)
14. Sadewasser, S., Schilling, J.S., Paulikas, A.P., & Veal, B.W., Pressure dependence of T_c to 17 GPa with and without relaxation effects in superconducting $\text{YBa}_2\text{Cu}_3\text{O}_x$. *Phys. Rev. B*, **61**, 741-749 (2000).
15. Mōri, N. *et al.*, Pressure dependence of superconducting transition temperature and of hall constant in high- T_c Cu-oxide superconductors. *Physica C*, **185-189**, 40-44 (1991).
16. McElfresh, M.W., Maple, M.B., Young, K.N., & Fisk, Z., Onset of superconductivity at 107K in $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ at high pressure. *Appl. Phys. A*, **45**, 365-368 (1988).
17. Jorgensen, J.D., et al., Pressure-induced charge transfer and dT_c/dP in $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$. *Physica C*, **171** 93-102 (1990).
18. Shannon, R.D. Dielectric polarizabilities of ions in oxides and fluorides. *J. Appl. Phys.*, **73**, 348-366 (1993).
19. Shannon, R.D. Revised Effective Ionic Radii and Systematic Studies of Interatomic Distances in Halides and Chalcogenides. *Acta. Crystallogr. A*, **32**, 751-767 (1976).